

RESEARCH PAPER

## Hydroxyapatite-Hardystonite nanocomposite scaffolds prepared by the replacing the polyurethane polymeric sponge technique for tissue engineering applications

Behrooz Aghajani <sup>1\*</sup>, Ebrahim Karamian <sup>2</sup>, Behnam Hosseini <sup>3</sup>

<sup>1</sup> Faculty of Materials Engineering, Shahreza Branch, Islamic Azad University, Shahreza, Iran

<sup>2</sup> Advanced Materials Research Center, Faculty of Materials Engineering, Najafabad Branch, Islamic Azad University, Najafabad, Iran

<sup>3</sup> Young Researchers and Elite Club, Shahreza Branch, Islamic Azad University, Shahreza, Iran

### ABSTRACT

**Objective (s):** Silicate bioceramics containing Zn and Ca like hardystonite (Hr) with chemical formula  $\text{Ca}_2\text{ZnSi}_2\text{O}_7$  has attracted the attention of researchers in biomedical field due to its remarkable biological and mechanical properties. The new generation of bioceramics can applied in bone tissue engineering to substitute with infected bone. However, these zirconium-silicate bioceramics have proper features; they can be used as additive with calcium phosphates (CaPs) like hydroxyapatite (HA). These composite may enhance the weak properties of pure HA powders.

**Materials and Methods:** In the current study, the Hr powder with sol-gel method was synthesized. Then, hydroxyapatite-hardystonite (HA/Hr) scaffolds with various amount of Hr in HA (0, 5, 10, and 15 wt. %) were prepared by the replacing the polyurethane polymeric sponge technique. Then, the ceramic scaffolds were sintered at 1150°C for 3 hours. The result of the scaffold nanocomposite specimens were tested for compressive strength and bioactivity behaviour. The phase and morphology of the specimens were analysis with X-ray Diffraction (XRD) and Scan Electron Microscope (SEM) techniques.

**Results:** The bioactivity, sinterability and compressive strength (CS) properties of HA-Hr scaffold nanocomposite has been developed by addition of 15 wt. % Hr in HA matrix. The results showed the scaffold nanocomposite containing 15 wt. % Hr have the highest value of CS which is equal 1.21 MPa. Our data indicate that Hr ceramics possess proper mechanical properties as compared to pure HA, and may possess good biocompatibility in biological analysis.

**Conclusion:** The study indicates that scaffold containing 10 wt. % Hr had proper bioactivity behaviour which leads the scaffolds surface to form bone-like apatite on the surface of scaffolds.

**Keywords:** Hydroxyapatite, Hardystonite, Nanocomposite, Scaffolds, Tissue Engineering

### How to cite this article

Aghajani B, Karamian E, Hosseini B. Hydroxyapatite-Hardystonite nanocomposite scaffolds prepared by the replacing the polyurethane polymeric sponge technique for tissue engineering applications. *Nanomed J.* 2017; 4(4): 254-262. DOI: [10.22038/nmj.2017.04.008](https://doi.org/10.22038/nmj.2017.04.008)

### INTRODUCTION

Bone tissue engineering is a field that helps the biomaterials engineer to design artificial bone in case of fracture bones caused by accident and tumors [1]. Using bone auto grafts, allograft, and xenografts from human and animal source help to heal the tissue as one of common tissue engineering technique. Recently various types of calcium phosphates (CaPs) have been introduced

to apply in tissue engineering application [2]. However; these CaPs have some weak properties like improper mechanical (brittleness) and chemical stability in their structure [3]. One of the most important characteristic of has like porosity and cells transformation of artificial bone play a significant role in the bones regeneration of implanted tissue. The scaffolds porosity is influenced by the architecture of scaffold and materials characteristic in the range of 100  $\mu\text{m}$ . The repair of bone defects consider as a major clinical challenge all around the world. One of the known

\* Corresponding Author Email: [aghajaniBehrooz@yahoo.com](mailto:aghajaniBehrooz@yahoo.com)

Note. This manuscript was submitted on August 16, 2017; approved on September 15, 2017

CaPs is hydroxyapatite (HA) which has a potential ability to substitute with human's bones [4-5]. Sadeghzade et al [4]. fabricated pure hardystonite ( $\text{Ca}_2\text{ZnSi}_2\text{O}_7$ ) nanopowder by combustion synthesis method. Their result indicated that mean particle size and the maximum crystallite size of the produced hardystonite nanopowder were almost 40 nm, respectively. Nevertheless, CaPs have some drawback like safety refusal and tissues may have some necrosis. Several bioceramics add to HA to enhance its properties like  $\text{TiO}_2$  [1, 3],  $\text{ZrO}_2$  [6-7], diopside [8-11], baghdadite [12, 20], hardystonite [13, 28] and etc. Zinc as one of the crucial trace element that also plays an important role in bone metabolism [4, 13]. Ceramics containing Zn salt have good property as a substituted tricalcium phosphate (TCP) and enhance the range of apatite formation in the implants [14, 19]. An hardystonite is a mineral containing Ca, Zn, and Si, with a melting temperature of 1425 °C and a density of 3.40 g/cm<sup>3</sup>, and so far has no important industrial applications [13-14]. While Zn-incorporated to calcium silicate (e.g. Hr) with chemical formula  $\text{Ca}_2\text{ZnSi}_2\text{O}_7$  can have better mechanical and strength properties [14, 28-29]. Recently, the new generation of silicate bioceramics like akermanite [15], diopside [8-11] hardystonite [11, 20], baghdadite [12], nanoclay [11, 18] and bredigite [11, 28] has been explained by researchers [13-18, 28]. In another study, Karamian et al [21]. investigated hydroxyapatite-baghdadite scaffold nanocomposite coated by PCL/Bioglass with polyurethane polymeric sponge technique [20]. They showed that addition of baghdadite can enhance the HA mechanical and biological properties dramatically. In this study HA-Hr nanocomposite scaffolds has been fabricated. A series of tests like bioactivity, and mechanical testing were carried out to analyse their physico-chemical and biological properties to HA-Hr scaffolds. The aim of the current project was to prepare nanostructured HA/Hr scaffolds nanocomposite by replica method using polyurethane foam. The mechanical and biological properties of scaffold nanocomposite were discussed and the optimum sample were selected for bone tissue engineering applications.

## MATERIALS AND METHODS

### Hydroxyapatite preparation

In this study, bovine bones were used for base matrix ceramic. The bovine bone/natural

HA was boiled for 10-12 h to remove flesh and fat according to the previous study [2]. The bones were dried at 110°C for several hours to remove moisture. To prevent blackening with soot during heating, the bones are cut into small pieces of about 10 mm thick and heated at 500 °C (bone ash) for 2 h in air to allow for evaporation of organic substances. The resulting black bone ash was heated for 3 h at 850°C. This synthesis is called thermal decomposition of bone resource to create natural HA, NHA as described in our previous work [2-3].

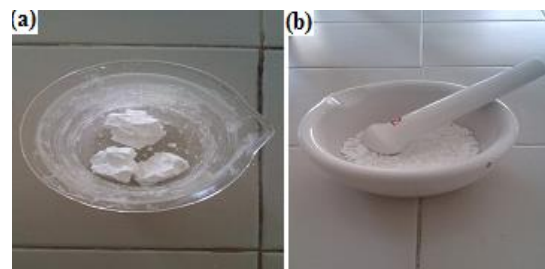


Fig. 1. Natural Hydroxyapatite powder using in the scaffolds nanocomposite a) agglomerated HA, and b) HA powder after high energy ball milling

### Hardystonite preparation

Hardystonite powders were prepared by the sol-gel process using tetraethyl orthosilicate (TEOS), zinc nitrate hexahydrate and calcium nitrate tetrahydrate as raw materials. Briefly, the Hr fabricated according to the previous work [22, 29]. The TEOS was mixed with water and 2 M  $\text{HNO}_3$  (mol ratio:  $\text{TEOS}/\text{H}_2\text{O}/\text{HNO}_3=1:8:0.16$ ) and hydrolyzed for 30 min under stirring. Then, the  $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  and  $\text{Ca}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$  were added into the mixture (mol ratio:  $\text{TEOS}/\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}/\text{Ca}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O} = 2:1:2$ ), and reactants were stirred for 5 h at room temperature. After the reaction, the solution was maintained at 60°C for 1 day and dried at 120°C for 2 days to obtain the dry gel. The dry gel was ground and sieved to 250-mesh, transferred into a corundum crucible and calcined at 1100 and 1200°C for 3 h, respectively.

### Hydroxyapatite-hardystonite nanocomposite preparation

The prepared HA composite with Hr with (0 wt.%, 5 wt.%, 10 wt.%, and 15 wt.%). Then the produced nanocomposite powders was mechanically activated through high energy ball milling for 60 min to gain pure and homogenised nanocomposite distribution of additive in matrix. To evaluate sinterability, green bodies of

hardystonite of about 10 mm×12 mm in size were prepared and fired from 1250°C to 1350°C. The sintered hardystonite ceramics were analyzed by XRD and SEM technique. Fig 1 indicate the agglomerated HA before ball milling and after high energy ball milling. The agglomerated HA particles indicated that after some hours purified and The BPR was 10 and the speed of vial was 600 rpm. The nanocomposite powder then pressed under 60 MPa pressure and the obtained samples were sintered through two step sintering (TSS) process, as shown in Fig. 2.

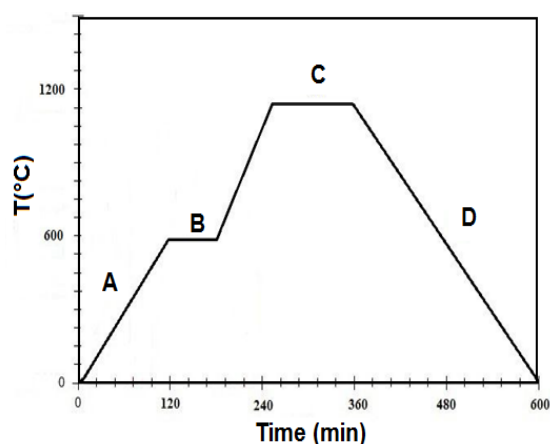


Fig. 2. The Two Step Sintering (TSS) process to develop the materials strength

#### **Polyurethane polymeric sponge technique**

To prepare HA-Hr scaffold nanocomposite the replica method using polyurethane foam was utilized. The scaffolds nanocomposite were combined with different concentration of Hr, 0, 5, 10, 15 wt. %. In addition, 1 wt. % sodium tripolyphosphate (STPP) and 1 wt. % Carboxymethyl cellulose were used as a dispersing and binder agent, respectively, during preparation of the ceramic slurry containing HA- Hr. Finally, the scaffolds were sintered at 1350°C for 2 h with the heating and cooling rate of 10°C/min.

#### **Compressive strength test**

Compressive strength was determined by crushing cylindrical specimens of dimensions 10 × 20 mm (diameter thickness) using a computer-controlled universal testing machine (Instron 8874, UK) with a ramp rate of 0.5 mm min<sup>-1</sup>. The ASTM standard No. C0020–00R05 is used to evaluate the cold crushing strength of the produced samples. The samples were tested and replicated

for three time in both biological and mechanical investigations.

#### **Bioactivity test**

In order to evaluate the apatite formation ability of the HA-Hr scaffold nanocomposites, simulated body fluid (SBF) was used which is described by Kokubo et al. [23]. Cylindrical scaffolds nanocomposite with dimension of 10×12 (diameter × height) were soaked in 12 cc SBF in the falcon tube for 28 days and kept in benmary bath with circulatory water at 37°C.

#### **Chemical changes test**

The pH of the solution was measured every two days by a pH meter. In addition, changes in element concentration of SBF were also measured by inductively coupled plasma (ICP) method (Equipment Model, and Zaies).

#### **Materials characterization**

##### **X-Ray diffraction (XRD) analysis**

X-ray diffraction (XRD) is carried out for structural identification of the pure NHA and NHA-Hr containing various amount of Hr in HA matrix. XRD patterns are recorded with a Bruker AXS Germany make X-ray diffractometer, having  $\text{CuK}\alpha$  ( $\approx 1.5405 \text{ \AA}$ ) incident radiation. The XRD peaks are recorded in 2 theta range of 20–60°. The phase characterization of the NHA and NHA/Hr 20 wt.% nanocomposite was done X-ray diffractometer (X' pert Philips) with  $\text{CuK}\alpha$  radiation ( $\lambda = 0.154 \text{ nm}$ ) (IAUN, Isfahan, Iran). The XRD traces were recorded in the 2θ range of 10–90°.

##### **Scan electron microscopy (SEM) analysis**

The surface morphology and microstructure of the samples before and after incubation is visualized by means of Scanning Electron Microscopy (JSM/JEOL-6360). All the samples are coated with thin film of gold (Au) to reduce charging of the sample. Simultaneously the elemental compositions of the samples are analysed using Energy Dispersive Spectroscopy (EDX). Also, the EDX analysis was utilized for more precise comparison of the amount of apatite formation in the sintered samples soaked in the SBF for certain period of time.

##### **Thermogravimetric analysis (TGA)**

Thermogravimetric analysis or thermal gravimetric analysis (TGA) is a method of thermal

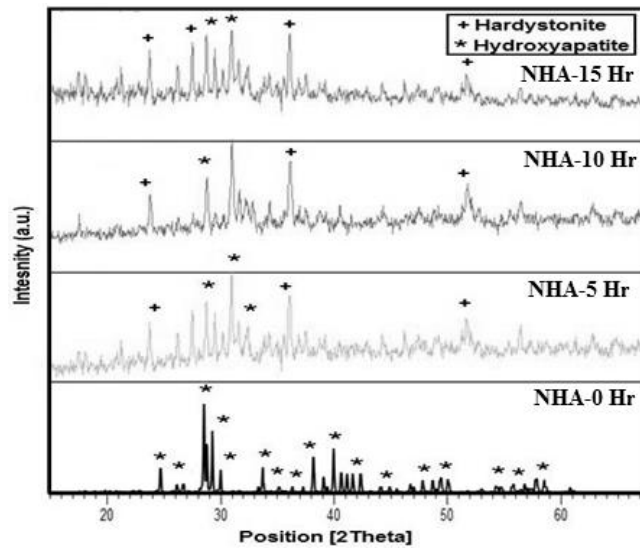


Fig. 3. XRD patterns of Hr powder using in the scaffolds

analysis in which changes in physical and chemical properties of materials are measured as a function of increasing temperature (with constant heating rate), or as a function of time (with constant temperature and/or constant mass loss).

## RESULTS AND DISCUSSIONS

### XRD Results

Fig 3 shows the XRD patterns of NHA powder. In the current work, the sample just heated at 850°C to fabricate NHA powders. As depicted in Fig 3-a all the peaks belong to HA phase and there is not any extra phase as impurities. Fig 3(b-d) represented the XRD pattern of nanostructure HA/Hr nanocomposite powder containing 0, 5, 10, 15 wt. % Hr in NHA matrix. As it is seen, there are both phase's peaks, HA phase and Hr, in the XRD pattern. Also, in the other word, Fig 3 depicts the XRD patterns related to the complete synthesis of Hr at 1150-1200°C for more than 3 hours. As can be seen in this pattern, there is no impurity in Hr product. The XRD pattern of HA compared with the nanocomposite HA/Hr. The comparison indicated that as the Hr reinforcement added to HA, the XRD peaks tend to increase and the intensity reduce. Also, it is worth mentioning that in the sample containing 15 wt.% Hr the Hr peaks appear between 52-55°. In the sample with 15 wt.% Hr the sharp peak belongs to Hr appears between 25-30°. The XRD pattern indicated that as the Hr increase the materials crystallinity decrease.

Fig. 3 shows the XRD pattern of the ceramics

showing only the pattern of Hr. Fig. 3 shows the XRD patterns of the Hr powders prepared by this method. A strong Hr peak at about 31° 2θ was obvious in the XRD patterns of the powders calcined at 1100 and 1200°C, which indicated that the main resultant was Hr. The composite particles were prepared by blending HA and Hr particles in PCL solution. The ceramic particles were rarely visible on PCL fibers when observed under SEM. Recent advances in thermal spraying have revealed the ability to create oriented single crystals. The properties of these materials depend on the orientation of the crystals. Testing on such fine crystals is challenging; an easier approach would be to conduct testing on large single crystal [24-27].

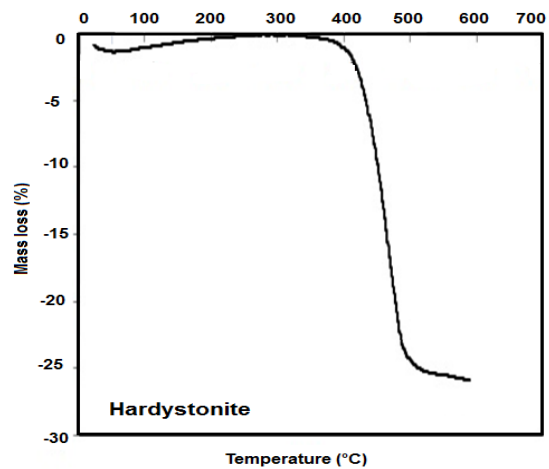


Fig. 4. TGA analysis of different Hr in air atmosphere

**TGA Results**

The bioceramic used in the present research convert, after heating in air, into highly reactive amorphous silica ( $\text{SiO}_2$ ). Their thermal decomposition behaviour in air was investigated using TGA analysis (see Fig. 4). The data indicate that the ceramic conversion occurs in the 350–650 °C, and is associated with a weight loss that ranges from 10 to 45%, depending on the specific silicone precursor. Another factors for lower modulus of HA scaffolds are the bigger size and lower surface charge of HA particles that led to agglomeration and reduction of mechanical property. The exact reason behind this is uncertain as all these

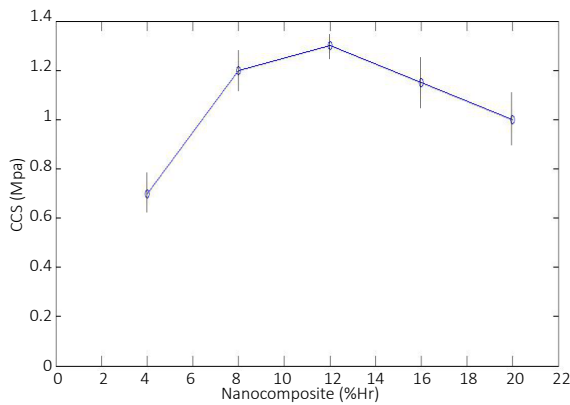


Fig. 5. Compressive strength of samples containing various amount of Hr in HA powder

mechanical properties exhibited by scaffolds are complex interplay between native properties, % crystallinity, inclusions, defects, fibre diameter, fibre arrangement etc., some of which may be resolved by individual fibre study which is beyond the scope of this study. The TGA results indicated that Hr loss its weight after 400°C for more than 20% because of water loss in Hr structure.

**Compressive strength of scaffold nanocomposite**

As it can be seen in Fig 5, as hardystonite amount increased the compressive strength and mechanical properties of the scaffold nanocomposite increased in all sample in the range of 0.8 to 1.2 MPa.

As it is shown as Hr amount increased the compressive strength of the scaffolds samples increased. The maximum useful increase in compressive strength can be for the sample with 10 wt. % Hr.

**SEM Results**

**Chemical changes of scaffold nanocomposite**

The surface morphology of the sintered Hr ceramics is shown in Fig.6. It can be seen that most Hr particles were sintered and some micropores were evident (Fig. 6a), The SEM indicated that the sintered Hr ceramics were not completely dense. The high magnification SEM micrograph shows that

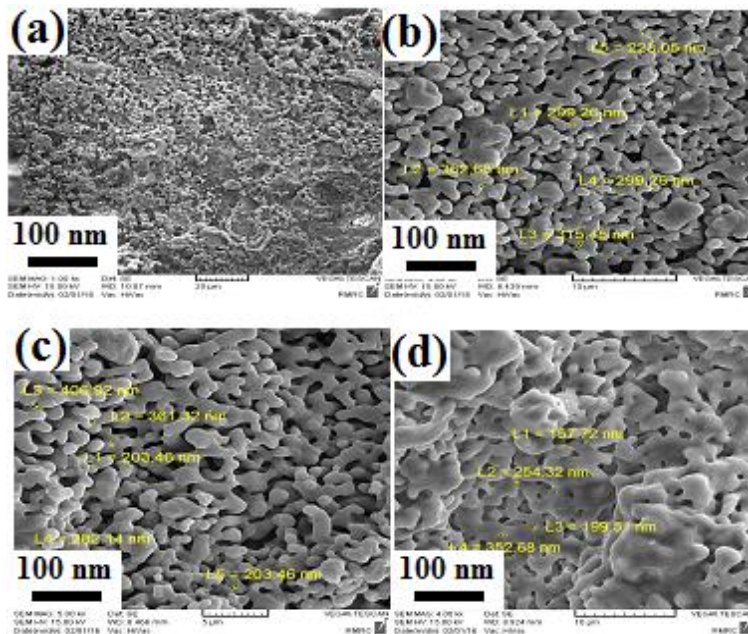


Fig. 6. SEM micrographs of HA/Hr scaffolds with different concentration of (a) 0 wt. % (b) 5 wt. % (c) 10 wt. % and (d) 15 wt.% Hr

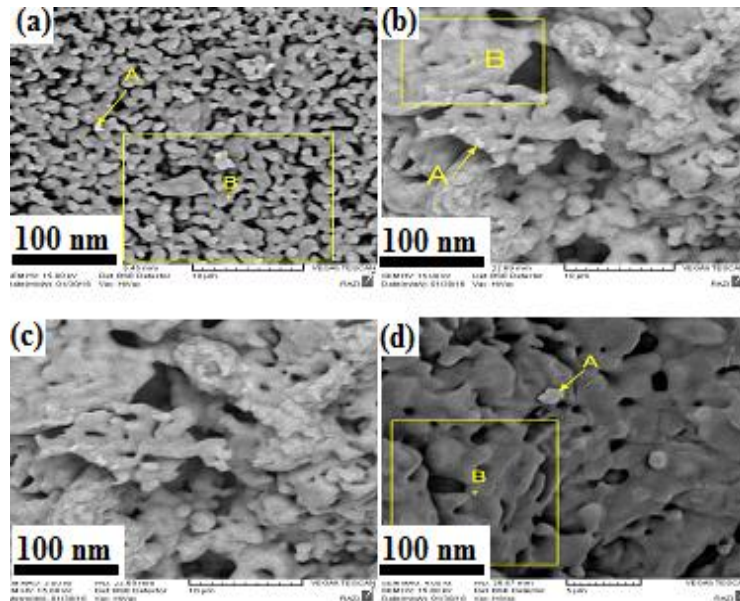


Fig. 7. SEM micrographs of HA/Hr scaffolds after soaking in SBF for 28 days with different concentration of (a) 0 wt. % (b) 5 wt. % (c) 10 wt. % and (d) 15 wt.% Hr

the grain size of Hr ceramics was about 1–5  $\mu\text{m}$  (Fig. 6b). Hr is a mineral, and the naturally occurring Hr was often not pure and associated with other minerals. To our knowledge, there was no report about chemical synthesis of pure Hr powders. Here we report a study on chemical synthesis of pure Hr powders by sol–gel method. The sintering process of scaffold nanocomposite NHA-Hr containing 0, 5, 10, 15 wt. % has been shown in Fig 6 (a-d). The SEM illustrated that as the amount of Hr increased the scaffold surface tends to be more glassy and amorphous. As the result of bioactivity evaluations shows the pH for the sample with Hr has a dramatic increase which is due to high degradation rate of HA (CaPs). The increase in  $\text{Ca}^{2+}$  amount (alkaline ion phase) cause the increase in pH value. After two weeks the Calcium Ion saturated in the solution and start to precipitated on the samples surfaces. Fig 7 illustrates the SEM micrographs of the scaffolds after soaking for 28 days in SBF solution. In higher magnification, plenty of bright precipitations (cauliflower) were observed on the surface of the scaffolds. As it is seen, by increasing Hr amount in the HA/Hr nanocomposite samples, Fig (7-d) is the comparison with the HA sample that shows increasing density of bright precipitations. It means that bioactivity has been increased by increasing of concentration of Hr and the ability to form and precipitate bone-like apatite as the

bright precipitations increased (Fig 7 (a-c)).

EDX point analysis has been done on the point A which shows in the SEM micrographs. It indicates that the bright precipitations are composition of Ca and P, Ca-P compounds. In fact, nucleation of the bright precipitations carries out on the Hr particles. Also, the result proved that  $\text{Si}^{+4}$  ions have very important role at the bright precipitations formation. Therefore,  $\text{Si}^{+4}$  ions leads to the formation of silanol (...Si–OH) group in the surface layer, a pH increase, and finally the production of a negatively charged surface with the functional group (Si–O). The prepared bio-layer on the surface of the samples leads to use the Calcium ion and a reduction in pH amount. As the HA amount in the nanocomposite increases the solution have more alkaline potential and increased pH. No difference in ALP activity was seen with the increase in concentration of either HA or HS. However, ALP activity of HS scaffolds significantly increased as compared to HA containing scaffolds, indicating the positive role of Zn and Si in bone metabolism. Our results also well support the role of these ions in bone metabolism; however does not give detailed insight into the mechanism of action of Zn and Si towards osteoblastic differentiation. To elucidate the mechanism of Zn and Si in osteoblastic differentiation, various studies are being carried

out but are not yet fully characterized. The EDX analysis of samples with 10% and 15% Hr (points A, B in Fig. 8c, d) are shown in Fig. 8.

As can be seen, the surface that the apatite layer has not been formed on it (point B), has a higher Ca concentration than the surface of apatite layer precipitated (point A). This confirms what was said in this study about the growth of the apatite layer. On the other hand, the samples with higher amount of Hr, have a more Si than the samples with a lower amount of Hr (see EDX analysis of point A for both percentage 10 wt.% and 15 wt.% of Hr). This is also confirms that with increasing the percentage of Hr up to 15, the Si-OH nucleation sites also increases lead to ease of formation of apatite layers. To study the degradation profile, scaffolds were immersed in PBS solution for two months at 37°C and the percentage mass loss of the scaffolds were measured at day 7, 28, 42 and 60. Fig. 8a clearly indicates that up to 28 days all scaffolds showed very less % mass loss. This happened due to presence of HA. Hr containing scaffolds led to faster degradation compared to HA containing scaffolds due to presence of Si whose superior bioactivity is well documented in literature.

On the other hand, Si ions in the Hr can form silanol groups on the surface of the scaffold (see Fig. 8). The formation of silanol groups induces a negative charge on the surface. Subsequently, the existing  $\text{Ca}^{2+}$  ions in the SBF can be adsorbed on the surface and consequently result in the deposition of calcium ions and the formation of an apatite layer on the surface of the scaffolds.

### Chemical changes evaluation

Fig 9 shows the results of the ICP, elemental chemical results, of SBF containing the scaffolds. Decreasing of the percentage of Si ion in solutions containing more Hr powder samples indicates the presence of higher amount of Si element and it works as actively for formation Ca/P compounds precipitations. In fact, this element, Si ions, role very important at formation Ca/P compounds precipitations on the surface scaffolds. As an interesting biomaterial with potential orthopaedic and dental applications HA as good mechanical properties, osteoconductivity, bioactivity, and bone bonding ability. HA is not biodegradable and can be removed and remodelled in the host. If implanted directly, it may dislocate within the tissue. In fact, the nucleation was grown on Hr particles.

When the amount of Hr reaches to 15 wt%, the density starts to decrease. This is attributed to the overlapping of glass bonds and their subsequent failure. In all percentages of Hr (0, 5, 10, 15 and 20 wt.%), the pH value of the samples has increased during the first week of experiments. Higher concentration of Ca ions in the natural hydroxyapatite in comparison with non-natural one led to the movement of the calcium ions into the solution and the increase of pH value. Fig 10 indicated the ICP analysis of the NHA-Hr scaffold nanocomposite calcium ions concentration in the SBF solution for the sample containing 20 wt.% Hr has been recorded about 142 ppm. The reason for this reduction can be absorption of the calcium ions to the scaffolds surface which

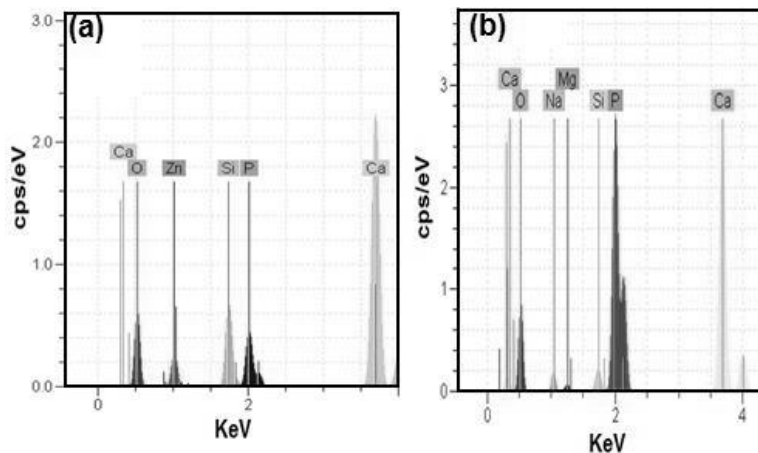


Fig. 8. EDX micrographs of HA-Hr scaffolds after soaking in SBF for 28 days with different concentration of (a) 0 wt. % and (b) 10 wt. % Hr

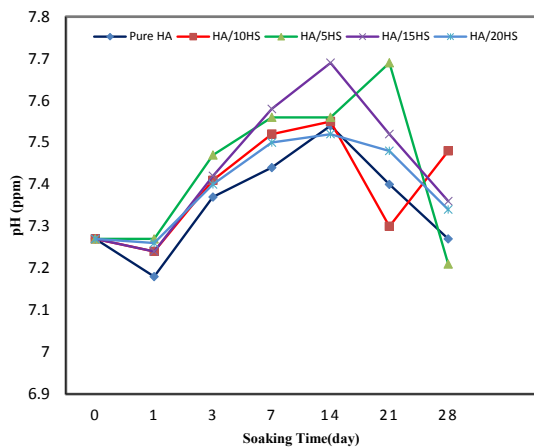


Fig.9. Change of pH value in SBF solutions of the samples in the during 28 days

leads to apatite formation. In sample containing 10 wt.% Hr the calcium ions was about 142 ppm. Also, the results showed that decrease in Zn ion regarding to the increasing of Hr can be define as precipitation of Zn ion on the scaffold surface for bone like apatite preparation. Zn ion have an important role as a germinator on the apatite surface. In addition Fig 10 showed that decreasing in Si ions in the sample with 20 wt.% Hr can be because of high degradation rate of Si ions.

### CONCLUSION

Pure Hr ( $\text{Ca}_2\text{ZnSi}_2\text{O}_7$ ) powders were synthesized by the sol-gel method and Hr ceramics were prepared by sintering powder compacts. Best results were obtained at 1350°C for 5 h, where the compressive strength 1.21 MPa. The nanocomposite samples with 10wt. %HT have the maximum value of the density, which is attributed to the formation of Hr silicate phases between the matrix particles and subsequently the formation of glass bonds. A maximum value of 1.21 MPa was obtained for the compressive strength of HA-10 wt% HT nanocomposite sample.

### ACKNOWLEDGEMENTS

The authors would like to extend their gratitude for the support provided by the Najafabad branches of Islamic Azad University, Isfahan, and Iran.

### CONFLICT OF INTEREST

The authors confirm that this article content has not any conflicts of interest.

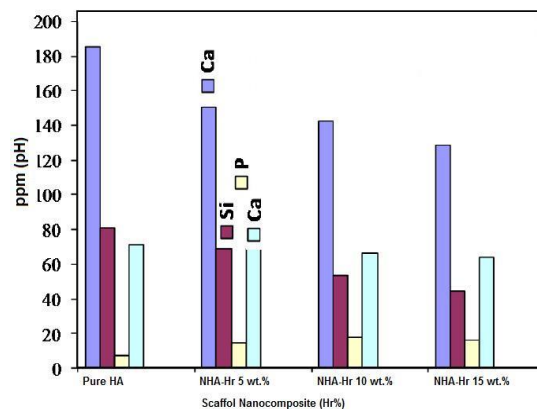


Fig.10. Ions changes in SBF solutions of the samples in the during 28 days

### REFERENCES

- 1.Khandan A, Karamian E, Bonakdarchian M. Mechanochemical synthesis evaluation of nanocrystalline bone-derived bioceramic powder using for bone tissue engineering. Dent Hypotheses. 2014; 5(4):155.
- 2.Karamian E, Khandan A, Eslami M, Gheisari H, Rafiaei N. Investigation of HA nanocrystallite size crystallographic characterizations in NHA, BHA and HA pure powders and their influence on biodegradation of HA. Adv Mat Res. 2014; 829: 314-318.
- 3.Karamian E, Abdellahi M, Khandan A, Abdellah S. Introducing the fluorine doped natural hydroxyapatite-titania nanobiocomposite ceramic. J Alloy Compd. 2016; 679: 375-383.
- 4.Sadeghzade S, Emadi R, Tavangarian F. Combustion assisted synthesis of hardystonite nanopowder. Ceram Int. 2016 31; 42(13): 14656-14660.
- 5.Karamian EB, Motamedi MR, Mirmohammadi K, Soltani PA, Khandan AM. Correlation between crystallographic parameters and biodegradation rate of natural hydroxyapatite in physiological solutions. Indian J Sci Res. 2014 ;4(3): 092-9.
- 6.Karamian E, Motamedi MR, Khandan A, Soltani P, Maghsoudi S. An in vitro evaluation of novel NHA/zircon plasma coating on 316L stainless steel dental implant. Prog. Nat. Sci.. 2014; 24(2): 150-156.
- 7.Karamian E, Khandan A, Kalantar Motamedi MR, Mirmohammadi H. Surface characteristics and bioactivity of a novel natural HA/zircon nanocomposite coated on dental implants. Biomed Res Int. 2014; 2014.
- 8.Khandan A, Abdellahi M, Ozada N, Ghayour H. Study of the bioactivity, wettability and hardness behaviour of the bovine hydroxyapatite-diopside bio-nanocomposite coating. J Taiwan Inst Chem Eng. 2016; 60: 538-546.
- 9.Khandan A, Abdellahi M, Barenji RV, Ozada N, Karamian E. Introducing natural hydroxyapatite-diopside (NHA-Di) nanobioceramic coating. CeramInt. 2015; 41(9): 12355-12363.



10. Kazemi A, Abdellahi M, Khajeh-Sharafabadi A, Khandan A, Ozada N. Study of in vitro bioactivity and mechanical properties of diopside nano-bioceramic synthesized by a facile method using eggshell as raw material. *Mater Sci Eng C Mater Biol Appl.* 2017; 71: 604-610.
11. Abdellahi M, Najafinezhad A, Ghayour H, Saber-Samandari S, Khandan A. Preparing diopside nanoparticle scaffolds via space holder method: Simulation of the compressive strength and porosity. *J Mech Behav Biomed Mater.* 2017;72: 171-181.
12. Khandan A, Karamian E, Mehdikhani-Nahrkhalaji M, Mirmohammadi H, Farzadi A, Ozada N, Heidarshenas B, Zamani K. Influence of spark plasma sintering and baghdadite powder on mechanical properties of hydroxyapatite. *Procedia Mat Sci.* 2015; 11: 183-189.
13. Mohammadi H, Hafezi M, Hesarak S, Sepantafar MM. Preparation and characterization of Sr-Ti-hardystonite (Sr-Ti-HT) nanocomposite for bone repair application. *Nanomed j.* 2015; 2(3): 203-210.
14. Wu C, Chang J, Zhai W. A novel hardystonite bioceramic: preparation and characteristics. *Ceramint.* 2005; 31(1): 27-31.
15. Sharafabadi AK, Abdellahi M, Kazemi A, Khandan A, Ozada N. A novel and economical route for synthesizing akermanite ( $\text{Ca}_2\text{MgSi}_2\text{O}_7$ ) nano-bioceramic. *Mater Sci Eng C Mater Biol Appl.* 2017; 71: 1072-1078.
16. Jaiswal AK, Chhabra H, Kadam SS, Londhe K, Soni VP, Bellare JR. Hardystonite improves biocompatibility and strength of electrospun polycaprolactone nanofibers over hydroxyapatite: A comparative study. *Mater Sci Eng C Mater Biol Appl.* 2013; 33(5): 2926-2936.
17. Najafinezhad A, Abdellahi M, Ghayour H, Soheily A, Chami A, Khandan A. A comparative study on the synthesis mechanism, bioactivity and mechanical properties of three silicate bioceramics. *Mater Sci Eng C Mater Biol Appl.* 2017; 72: 259-267.
18. Heydary HA, Karamian E, Poorazizi E, Heydaripour J, Khandan A. Electrospun of polymer/bioceramic nanocomposite as a new soft tissue for biomedical applications. *Journal of Asian Ceramic Societies.* 2015; 3(4): 417-425.
19. Lu H, Kawazoe N, Tateishi T, Chen G, Jin X, Chang J. In vitro proliferation and osteogenic differentiation of human bone marrow-derived mesenchymal stem cells cultured with hardystonite ( $\text{Ca}_2\text{ZnSi}_2\text{O}_7$ ) and  $\beta$ -TCP ceramics. *J Biomater Appl.* 2010; 25(1): 39-56.
20. Karamian E, Nasehi A, Saber-Samandari S, Khandan A. Fabrication of hydroxyapatite-baghdadite nanocomposite scaffolds coated by PCL/Bioglass with polyurethane polymeric sponge technique. *Nanomed J.* 2017; 4(3): 177-183.
21. Cox SC, Thornby JA, Gibbons GJ, Williams MA, Mallick KK. 3D printing of porous hydroxyapatite scaffolds intended for use in bone tissue engineering applications. *Mater Sci Eng C Mater Biol Appl.* 2015; 47: 237-247.
22. Gheisari H, Karamian E, Abdellahi M. A novel hydroxyapatite-hardystonite nanocomposite ceramic. *Ceram Int.* 2015; 41(4): 5967-5975.
23. Kokubo T, Takadama H. How useful is SBF in predicting in vivo bone bioactivity?. *Biomaterials.* 2006; 27(15): 2907-2915.
24. Saber-Samandari S, Gross KA. Micromechanical properties of single crystal hydroxyapatite by nanoindentation. *Acta Biomaterialia.* 2009; 5(6): 2206-2212.
25. Gross KA, Saber-Samandari S, Heemann KS. Evaluation of commercial implants with nanoindentation defines future development needs for hydroxyapatite coatings. *J Biomed Mater Res B Appl Biomater.* 2010; 93(1):1-8.
26. Saber-Samandari S, Saber-Samandari S, Gazi M. Cellulose-graft-polyacrylamide/hydroxyapatite composite hydrogel with possible application in removal of Cu (II) ions. *React Funct. Polym.* 2013; 73(11): 1523-1530.
27. Saber-Samandari S, Alamara K, Saber-Samandari S, Gross KA. Micro-Raman spectroscopy shows how the coating process affects the characteristics of hydroxyapatite. *Acta biomaterialia.* 2013; 9(12): 9538-9546.
28. Khandan A, Ozada N. Bredigite-Magnetite ( $\text{Ca}_7\text{MgSi}_4\text{O}_{16}\text{-Fe}_3\text{O}_4$ ) nanoparticles: A study on their magnetic properties. *J Alloy Compd.* 2017; 726: 729-736.